


PLASKOLITE

**CONTINUOUS CAST
ACRYLIC SHEET
FABRICATION GUIDE**

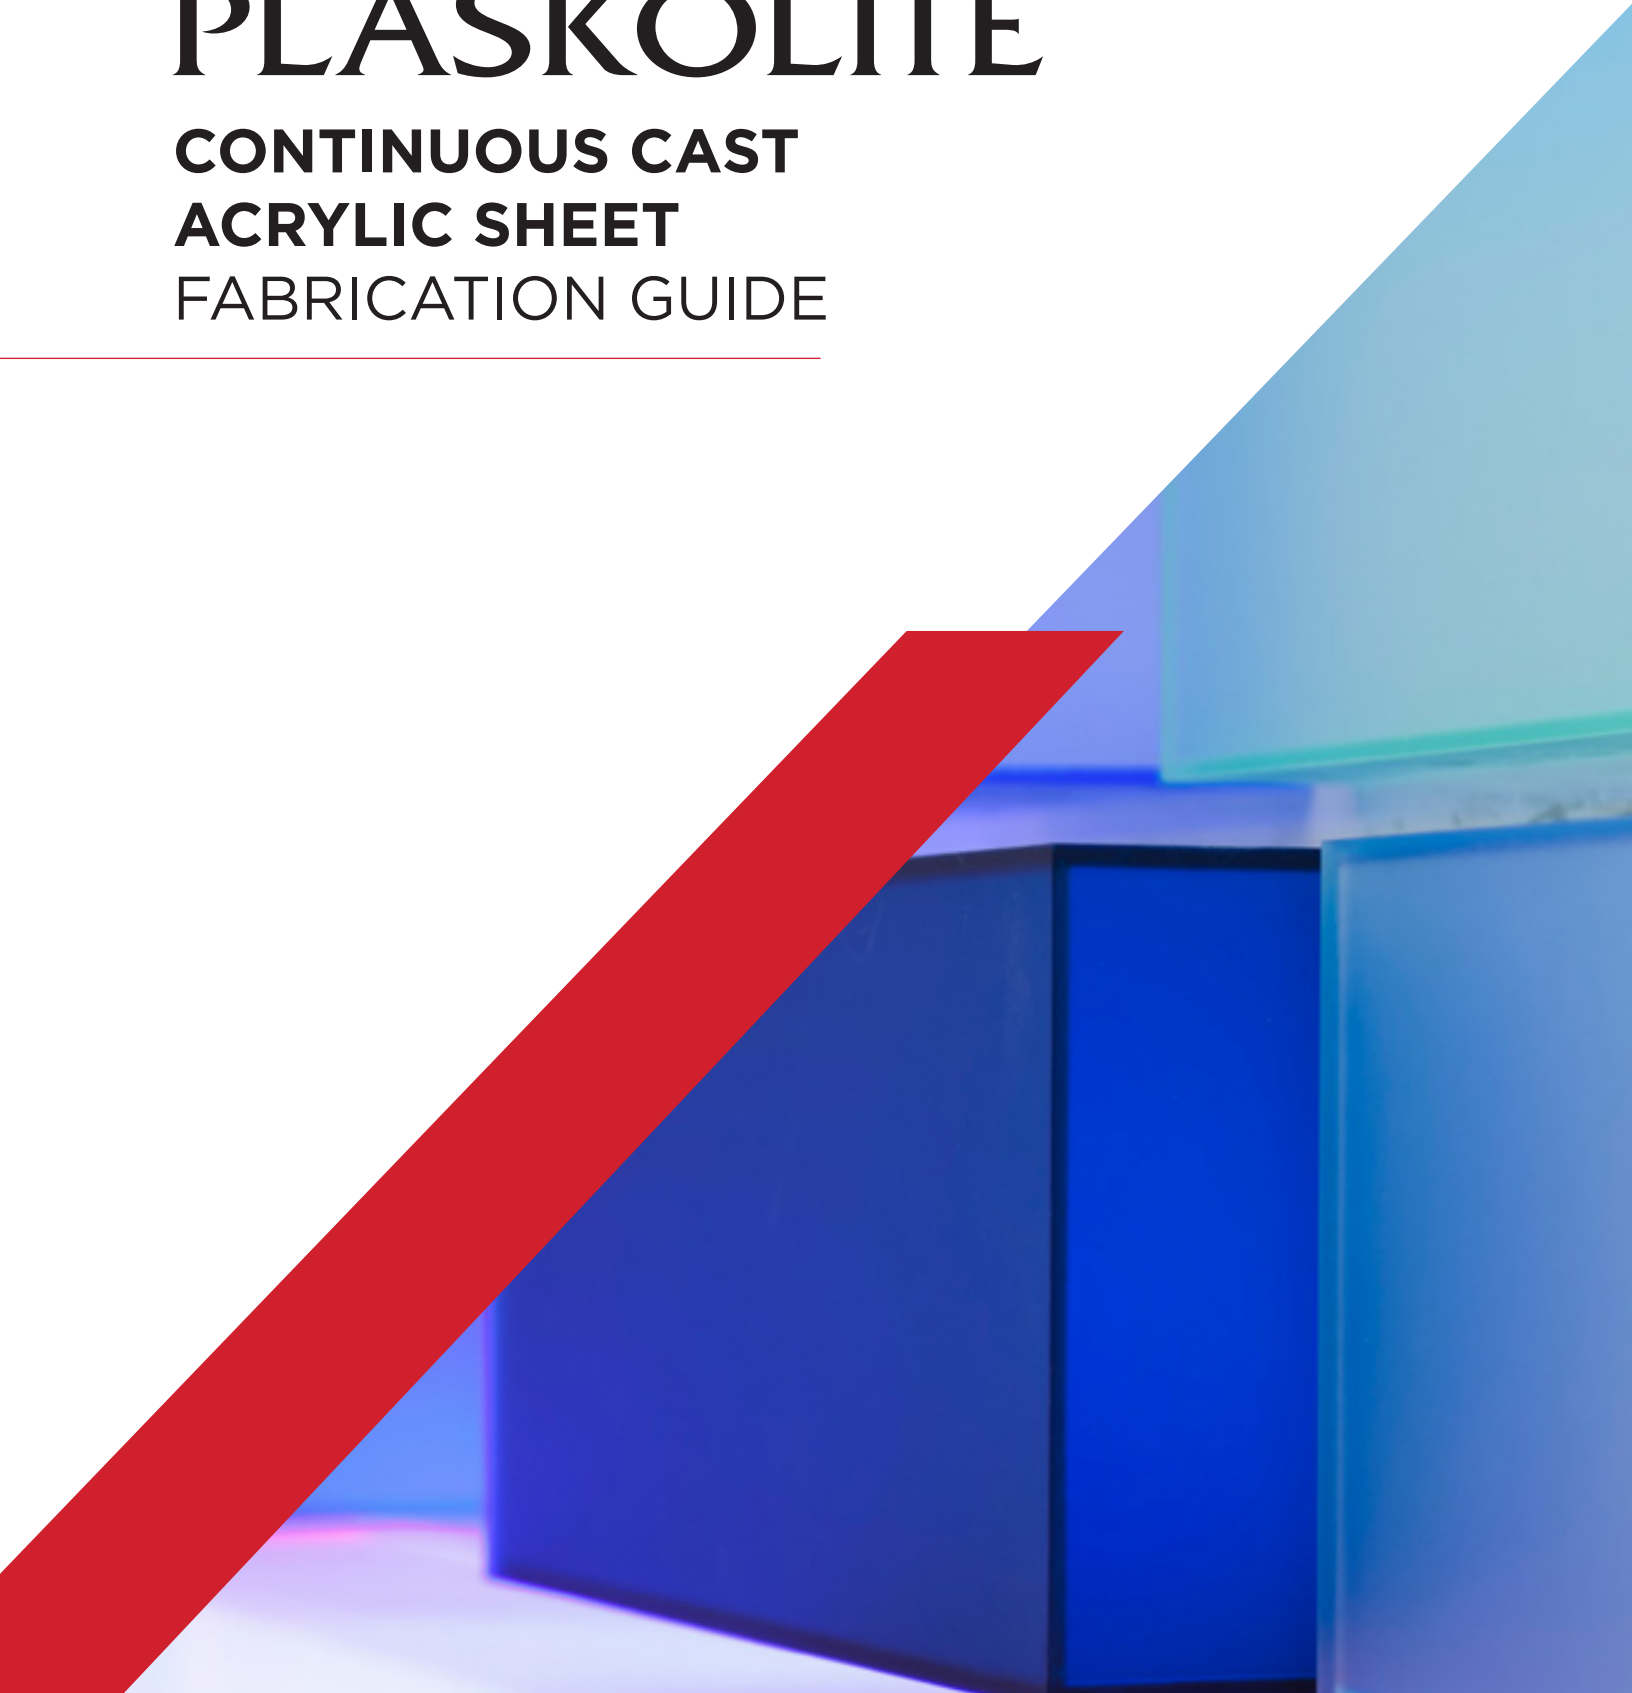

CONTENTS

3	—————	INTRODUCTION
4	—————	TYPICAL PROPERTIES
5	—————	GENERAL DESIGN CONSIDERATIONS
6	—————	HANDLING & STORAGE
7	—————	FABRICATION
8	—————	ARCHITECTURAL GLAZING
15	—————	DESIGN & FABRICATION SOLAR COLLECTORS
16	—————	STRIP HEAT BENDING & COLD FORMING
17	—————	LAYOUT
18	—————	CUTTING
20	—————	ROUTING
21	—————	LASER
23	—————	DRILLING
24	—————	THREADING & TAPPING
24	—————	BLANKING & PUNCHING
25	—————	CEMENTING
29	—————	MECHANICAL JOINING
29	—————	PAINTING & DECORATING
30	—————	FINISHING

INTRODUCTION

All information presented pertains to OPTIX®-L continuous cast acrylic sheet, previously known as Lucite® Lux. The data and information presented in this manual are concerned primarily with the design and fabrication of structures and components produced from OPTIX-L. This manual also presents concepts and principles necessary to develop functionally sound and attractive applications.

PROPERTIES

Continuous cast acrylic sheet has a unique combination of properties...outstanding weather resistance, brilliant clarity, "light-piping" and "edge-lighting" qualities, chemical resistance, smooth, easy-clean surface, and ease of forming and machining. Compared to other types of transparent thermoplastics, OPTIX-L acrylic sheet has outstanding resistance to the damaging effects of sunlight and outdoor weathering. The sheet offers excellent thickness tolerance for critical applications.

APPLICATIONS

The desirable properties of OPTIX-L continuous cast acrylic sheet account for its wide acceptance for many end-uses.

- Optical Qualities - Used as safety glazing in buildings and vehicles, instrument and equipment covers and machinery guards.
- Decorative - Enhances the functional and aesthetic beauty of exterior panels for appliances, exterior and trims for automobiles, and household and business accessories.
- Weather Resistance and Light Stability- With excellent ultraviolet (UV) light stability and resistance to weathering, the sheet is used extensively as safety glazing in outdoor signs and lighting fixtures as well as for indoor lighting panels and diffusers.

EASE OF FABRICATION

OPTIX-L continuous cast acrylic sheet can be easily fabricated using techniques currently practiced in the plastic industry. Parts made from the sheet can be machined, drilled, threaded and routed with standard wood and metal-working equipment. In addition, simple shapes can be formed to many configurations by thermoforming.



TYPICAL PROPERTIES

OPTIX-L CONTINUOUS CAST ACRYLIC SHEET*

Property	Test Method		
PHYSICAL			
Specific Gravity / Relative Density	ASTM D792	-	1.19
Optical Refractive Index	ASTM D542	-	1.49
Light Transmission - Total	ASTM D1003	%	92
Light Transmission - Haze	ASTM D1003	%	<1
Water Absorption	ASTM D570	%	0.20
MECHANICAL			
Tensile Strength	ASTM D638	psi	11,000
Tensile Modulus of Elasticity	ASTM D638	psi	465,000
Flexural Strength	ASTM D790	psi	14,700
Flexural Modulus of Elasticity	ASTM D790	psi	461,000
Izod Impact Strength - Notch	ASTM D256	ft-lb./in	0.32
Compressive Strength	ASTM D695	psi	83,300
Shear Strength	ASTM D732	psi	11,200
Rockwell Hardness	ASTM D785	-	M-100
THERMAL			
Maximum Recommended Continuous Service Temperature	-	°F	175
Deflection Temperature @ 264 psi	ASTM D648	°F	200
Coefficient of Linear Thermal Expansion	ASTM D969	in/in/°F	3.5 x 10 ⁻⁵
Thermal Conductivity	ASTM C177	Btu-ft/ft ² /hr/°F	0.12
Flammability (Burning Rate)	ASTM D635	in/min	1.18
Flammability	UL94	-	HB
Smoke Density Rating	ASTM D2843	%	13.5
Self-Ignition Temperature	ASTM D1929	°F	750
Flame Spread Index	ASTM E84	-	110
Smoke Developed Index	ASTM E84	-	530
ELECTRICAL			
Dielectric Constant @ 1 kHz	ASTM D150	-	3.0
Dielectric Constant @ 1 MHz	ASTM D150	-	2.7
Dielectric Strength	ASTM D149	V/mil	354
Volume Resistivity	ASTM D257	Ohms/cm	>3.91 x 10 ¹⁵

*Values provided should not be used for specification purposes. Some values will vary with sheet thickness.

GENERAL DESIGN CONSIDERATIONS

Proper design will have a major effect on product appearance, performance, and production cost. Perfectly flat surfaces should be avoided when practical. A very slight degree of curvature prevents minor aberrations which cause distorted reflections and related phenomena. Use of curved surfaces and/or ribs significantly increases the rigidity of a formed part. This added stiffness can have significant advantages in minimizing the support needed to hold the sheet in the end use application and during any secondary processing step.

OPTIX-L Continuous cast acrylic sheet will have a high gloss appearance. Although reinforced acrylic components can contribute to supporting loads, unreinforced sheet should not be used as a contributing support in a large or heavy structure. Constant exposure to high stress could result in eventual failure of the acrylic support.

In designing methods of assembly, force or pressure on the continuous cast acrylic sheet or component should be minimized. For example, this may be accomplished by oversizing drill holes, or by the use of special fasteners utilizing plastic or rubber grommets. A common assembly method uses a floating mount which allows the sheet to expand and contract without distortion, provided the mount is not clamped too tightly. Such a design, avoiding the use of holes and allowing the part to retain maximum strength, is the preferred method if it can be adapted to the particular application.

With unreinforced sheet, supports are sometimes used to minimize deflection caused by wind loads. Large sections may require several supports to distribute stress more evenly. In designing unreinforced or reinforced structures, standard methods of analysis may be applied. However, it is important to realize that the strength of any material is determined by a number of factors. There is a natural variability in the strength properties, depending on exact composition or fabricating method, post treatment and use environment. Developers of structural designs should recognize that reported product properties are typical values from which deviation is to be expected. Physical property data are obtained from specified tests under conditions that are only approximated in practice.

The elementary formula used in design is based on structural members having a constant cross-section. Such conditions are seldom attained in practice and the presence of shoulders, bosses, grooves, holes, threads, and corners results in a modification of the simple stress distribution, causing localized higher stress areas. This behavior is known as “stress concentration factor (K)”, where S_a is actual stress and S_c is calculated stress. **$K = S_a / S_c$**

Since continuous cast acrylics yield very little before failure, it is of particular importance to avoid local high stress concentration when designing with these materials.

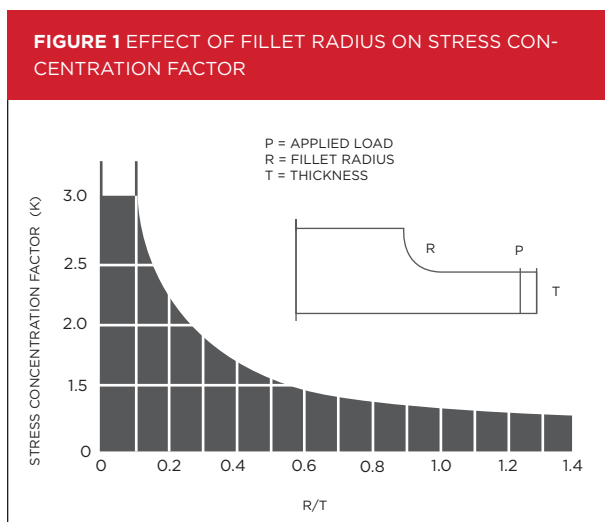


Figure 1 illustrates quantitatively the effect of fillet radius on stress concentration. Assume force “P” is exerted on the cantilever section shown. As the radius “R” is increased, with all other dimensions remaining constant, R/T increases proportionally, and the stress concentration factor has been reduced by 50% (3.0 to 1.5) by increasing the ratio of fillet radius to thickness six fold (from 0.1 to 0.6). Figure 1 illustrates how readily the stress concentration factor can be reduced by using a larger fillet radius. A fillet of optimum design is obtained with an R/T of 0.6. A further increase in radius reduces the stress concentration only a marginal amount.

Stress concentration factors of the same order of magnitude, as shown in Figure 1, have also been determined for grooves, notches, holes, screw thread, bosses, etc., in tensions and bending as well as in torsion.

A prototype is a good practical check on the design. Aesthetics are usually the most important aspects when working with parts fabricated from OPTIX-L continuous cast acrylic sheet. However, some mechanical or structural considerations are also required, usually in connection with assembly or fastening.

HANDLING AND STORAGE

MASKING

To provide protection during shipping, handling and storage, OPTIX-L continuous cast acrylic sheets are protected by paper replacement or polyfilm masking secured with a flexible adhesive. The masking is convenient for penciling in guidelines for sawing, drilling and other machining operations, and should be kept on the acrylic sheet through as many of the processing stages as possible. Paper replacement or polyfilm masking must, however, be removed before heating and forming. The masking can be removed by loosening one corner with a fingernail and peeling back the masking with a slow and steady pull or by rolling off on a tubular support. Acrylic sheet may be re-masked with the used masking which has been rolled up as a tube and kept clean and free from grit. The pressure-sensitive adhesive on the masking will retain its tackiness for several applications. If necessary, the masked sheets can be heated in an oven at 300°F (149°) for one minute or less in order to facilitate the removal of masking. If masking residue is seen after removing masking, wipe the sheet with a soft, grit-free cloth containing naphtha, isopropanol, kerosene, or vinegar (preferred), rinse with water afterwards. Some masking may become difficult to remove when exposed to the elements or when left on the product for long periods of time.

TECH NOTE: As a good practice, try to avoid starting & stopping when removing the masking. It is better to pull and remove in one swift motion to lessen the occurrence of masking residue on the sheet.

CAUTION: Both naphtha and isopropanol are very flammable, have relatively low flash points, and are easily ignited. Use only in a well-ventilated area and away from open flames and sparks. Follow the manufacturer's directions for safe handling.

STORING

OPTIX-L continuous cast acrylic sheet may be stored flat or stacked vertically in racks. The latter method eliminates the possibility that hard particles such as sharp-edged pieces of plastic, metal chips, sand or cinders to become lodged between the sheets. When stacked horizontally, the pressure of the sheets will force such particles into the plastic.

OPTIX-L will absorb moisture from the air. The absorption may cause the sheet to develop a temporary wavy appearance. Waviness will be relieved once the masking is removed and the product becomes fully acclimated. If a continuous cast acrylic sheet bows, as a result of improper storage, it can be straightened. Heat the sheet to just below the forming temperature 275°F - 290°F (135°C - 143°C) and place it on a smooth, flat surface. The flat surface should be covered with a nonlinting, soft cloth to prevent marring of the heated acrylic sheet and promote uniformity of cooling to reduce the risk of future warping.

FABRICATION

CLEANING

Abrasive cleaners and some window cleaning compounds will scratch the surface of continuous cast acrylic sheet. Do not use solvents such as methanol, toluene, acetone, chlorinated solvents, dry-cleaning solutions, lacquer thinners, gasoline, etc. since they may damage the surface. Ordinarily, dust and dirt can be removed with a soft, grit-free, nonlinting cloth dampened with clean water. Grease and oil deposits usually can be removed with naphtha or isopropyl alcohol. A soapy water mix is the preferred method of cleaning the sheet. Be sure to rinse well in order to remove any soapy residue.

CAUTION: Both naphtha and isopropyl alcohol are very flammable, have relatively low flash points, and are easily ignited. Use only in a well-ventilated area and away from open flames and sparks. Follow the manufacturer's directions for safe handling.

SAFETY

Safety goggles, gloves and other protective clothing should be worn when cutting, routing, drilling, threading, tapping, blanking or punching continuous cast acrylic sheet. The sheet can be machined in much the same manner as wood or soft metals such as brass, and can be hand-worked and cut with files, scrapers and hacksaws. Heated continuous cast acrylic sheet can be stamped, punched or sheared, as limited by thickness requirements.

The following general rules should be applied when continuous cast acrylic is machined.

- » Tools must be kept sharp, with nicks and burns eliminated from all cutting edges. Cutting tools and the part should always be supported firmly to prevent chattering and chipping. Machined areas of continuous cast acrylic which are ragged or chipped will provide notches where fracture or crazing can easily occur.
- » Hard, wear-resistant tools, such as those with tungsten carbide tips, are preferred because they retain their sharpness longer and provide better machined finish.
- » Cleanliness of machine and materials is very important in producing satisfactory work. It is often desirable to protect the surface of the sheet with masking during machining operations. Work areas should be kept free of sawdust, dirt, and chips which can scratch the sheets. Compressed air or vacuum can be used to remove such particles. Tables covered with a smooth hard material, such as "Formica®," are easy to keep clean and provide good working surfaces.
- » Since plastics have much lower thermal conductivity values than metals, thermoplastics tend to soften if excessive heat is generated during machining. Therefore, a coolant or a blast of air is sometimes required to dissipate heat from the continuous cast acrylic during machining operations.

ARCHITECTURAL GLAZING

OPTIX-L continuous cast acrylic sheet has high molecular weight and uniform thickness produced from virgin methyl methacrylate monomer. The sheet has outstanding optical properties, excellent weather resistance, uniform caliper control and high impact resistance. It has exceptional freedom from warpage, cracks, scratches, blisters, voids, foreign matter and other defects which may affect appearance or service ability. Continuous cast acrylic sheet is light weight and easily fabricated and may be ordered cut-to-size up to 108" x 240", in 0.118" in to 0.236" in, depending upon product type. These sheets are available in clear, solar tints, translucent whites and many additional colors.

APPLICATIONS

OPTIX-L continuous cast acrylic sheet is used where safety, light weight, optical clarity, and long-term retention of properties are important. Applications include glazing for institutional, industrial and commercial buildings, skylights and domes, shields and guards, lighting fixtures, solar panels and signage of all types.

INSTALLATION DETAILS RABBET DIMENSIONS

For outdoor use where large temperature variations may occur, OPTIX-L continuous cast acrylic sheet should be installed with a channel engaging the edges. Through-bolting or other inflexible mechanical fastenings are not recommended. The channel frame dimensions depend on sheet thickness, size of panes and design load. Small panes (major dimensions less than 24" in.) use minimum rabbet depth of 0.375" in. For intermediate and large size panes, see Table I.

TABLE I RABBET DIMENSIONS						
THICKNESS (IN.)	RABBET DIMENSIONS (IN.)			MAXIMUM SASH OPENING (IN.) PER DESIGN LOAD		
	DEPTH		WIDTH	20PSF	30PSF	40PSF
0.118	3/8	x	3/8	24 x 33	24 x 31	24 x 29
	1/2	x	1/2	24 x 45	24 x 42	24 x 39
0.177	1/2	x	7/16	42 x 42	40 x 40	39 x 39
	3/4	x	7/16	30 x 45	30 x 43	30 x 41
		36 x 77		36 x 71	36 x 65	
		48 x 71		48 x 63	48 x 57	
0.236	1/2	x	1/2	44 x 44	42 x 42	41 x 41
		30 x 46		30 x 45	30 x 43	
	3/4	x	1/2	60 x 72	60 x 65	60 x 60
		36 x 84		36 x 78	36 x 72	
	1.0	x	5/8	48 x 114	48 x 106	48 x 98
				60 x 108	60 x 96	60 x 90

SEALING DETAILS

Sealants and tapes should have sufficient extensibility to accommodate thermal expansion and contraction. The sealants should adhere to both the OPTIX-L continuous cast acrylic sheet and the frame. For small panes (less than 24" in. major dimensions), use non-hardening glazing compound or use butyl tapes. For intermediate and large size panes, use butyl tapes (intermediate size only) or use suggested sealants. Table II and Table III indicate recommended sealant and tape size.

TABLE II SEALANT SIZE					
THICKNESS (IN.)	LONG DIMENSION (IN.)	SEALANT DIMENSIONS (IN.)		FILLER TAPE DIMENSIONS (IN.)	
		DEPTH	WIDTH	DEPTH	WIDTH
3/16	UP TO 72	1/4	1/4	1/2	1/4
1/4	72 TO 108	1/4	3/8	3/4	3/8
1/4	108 TO 120	1/4	1/2	7/8	1/2

TABLE III RECOMMENDED SEALANTS		
SEALANT TRADE NAME	TYPES	MANUFACTURER
DOWSIL 732	SILICONE RUBBER	DOW CORNING
SILGLAZE II	SILICONE RUBBER	GE SILICONES/MOMENTIVE PERFORMANCE MATERIALS
ULTRAGLAZE	SILICONE RUBBER	GE SILICONES/MOMENTIVE PERFORMANCE MATERIALS
RTV 5818	SILICONE RUBBER	GE SILICONES/MOMENTIVE PERFORMANCE MATERIALS
WEATHERBAN 202	SYNTHETIC ELASTOMER	3M COMPANY
MONO	ACRYLIC TERPOLYMER	TREMCO MFG. COMPANY

THE MANUFACTURERS' RECOMMENDATIONS SHOULD BE FOLLOWED WHEN USING THESE SEALANTS

THERMAL EXPANSIONS

Table IV shows the recommended thermal expansion clearances for OPTIX-L continuous cast acrylic sheet. The height and width should be cut shorter than the overall sash dimensions by the amount shown in Table IV. Care should be taken to ensure smooth cut edges, thereby avoiding stress-producing notches.

TABLE IV EXPANSION CLEARANCE OPTIX-L CONTINUOUS CAST ACRYLIC SHEET	
LENGTH (IN.)	EXP. (IN.)
up to 36	1/8
36 to 60	1/4
60 to 96	3/8
96 to 120	7/16

INSTALLATION DETAILS SHEET PREPARATION

- » Use a sharp saw blade to cut sheet to desired size.
- » Unmask sheet immediately before installation.
- » Clean cut edges thoroughly before setting in sash.
- » Excessive sealant smears should be avoided. Paper-backed adhesive tape can be used around the edges adjacent to the rabbets to avoid smears.

SASH PREPARATION



- » Clean sash surfaces to remove dirt and oil.
- » The sash rabbet should be free of burrs.
- » Use recommended primer from the sealant manufacturer to ensure proper adhesion.

FACE GLAZING

- » See Figure II for installation detail.
- » Use elastic glazing compound only.
- » Apply back sealant to the rabbet and bed the OPTIX L continuous cast acrylic sheet centered in the sash.
- » Fasten with glazing points or clips, apply face sealant, and trim the caulking bead.

STANDARD AND CUSTOM SASH GLAZING

OPTIX-L continuous acrylic sheet can be set directly on sill; it is not necessary to use setting blocks. Install butyl tape and/or sealant according to manufacturer's recommendations. See Figure II and Figure III for more details.

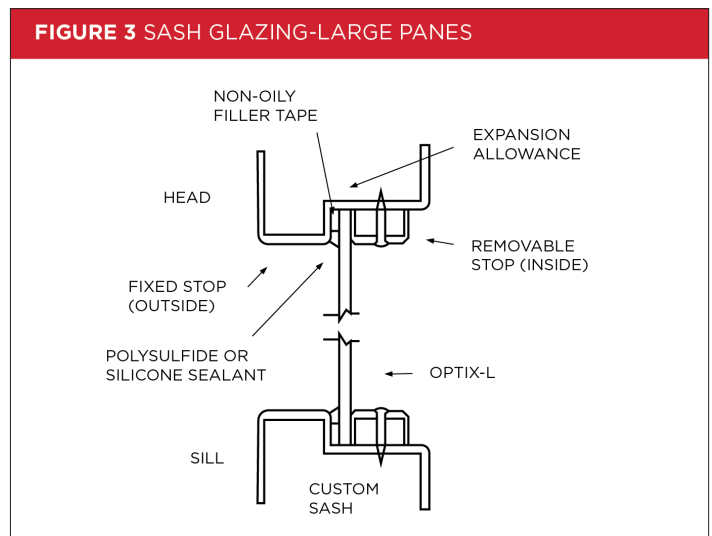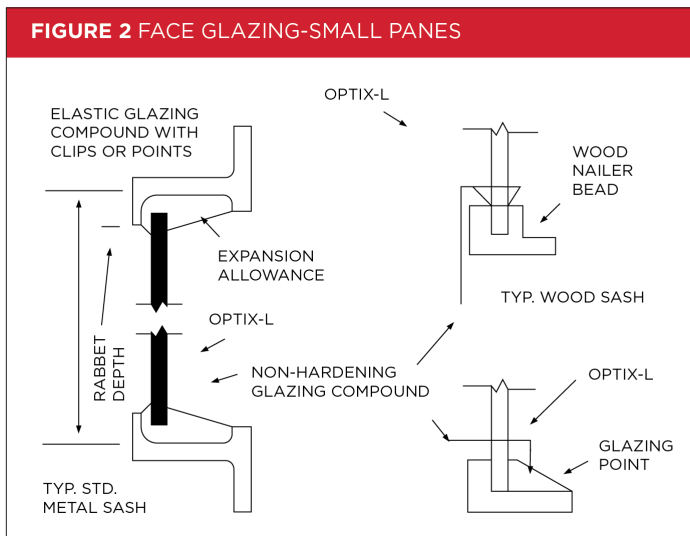

DESIGN CONSIDERATIONS

OPTIX-L continuous cast acrylic sheet undergoes dimensional change due to thermal expansion and contraction. (see Table V) Through-bolting or use of other inflexible mechanical fasteners which do not provide for expansion or contraction may cause failure of the installation.

TABLE V COMPARISON OF COEFFICIENTS OF THERMAL EXPANSION	
INCH/INCH/°F	
OPTIX-L CONTINUOUS CAST ACRYLIC SHEET	0.0000390
ALUMINUM	0.0000129
STEEL	0.0000063
FLOAT GLASS	0.0000050

CHEMICAL RESISTANCE

OPTIX-L continuous cast acrylic sheet is unaffected by a wide variety of chemicals and cleaning agents, including diluted solutions of acids and alkalis, petroleum oils, aliphatic hydrocarbons and dilute alcohols. However, gasoline, chlorinated solvents, acetone, or denatured alcohol should never be used to clean OPTIX-L, as these solvents tend to soften the acrylic surface and may cause crazing.

TABLE VI CHEMICAL RESISTANCE				
COMPOUND CLASS	COMMON NAME	TYPE	CONCENTRATION %	CHEMICAL RESISTANCE AT 72° F*
ACIDS	ACETIC ACID	GLACIAL	100	NR
	ACETIC ACID		5	E
	CHROMIC ACID		40	F
	CITRIC ACID		10	E
	HYDROCHLORIC ACID	CONCENTRATED	38	E
	HYDROCHLORIC ACID		10	E
	NITRIC ACID	CONCENTRATED	70	F
	NITRIC ACID		40	G
	NITRIC ACID		10	E
	OLEIC ACID			E
	SULFURIC ACID	CONCENTRATED	98	NR
	SULFURIC ACID		30	E
	SULFURIC ACID		3	E
BASES	AMMONIA	SOLUTION	35	E
	AMMONIA		28	E
	AMMONIA		10	E
	SODIUM CARBONATE		20	G
	SODIUM CARBONATE		2	G
	SODIUM HYDROXIDE		60	E
	SODIUM HYDROXIDE		10	E
	SODIUM HYDROXIDE		1	E
	HYDROGEN PEROXIDE		10	E
	COMMERCIAL PRODUCTS	COTTONSEED OIL	EDIBLE GRADE	
DETERGENT SOLUTION		HEAVY GRADE	0.025	E
KEROSENE		NO. 2 FUEL OIL		G
GASOLINE				F
LACQUER THINNER				NR
MINERAL OIL		WHITE, USP		F
OLIVE OIL		EDIBLE GRADE	1	E
SOAP SOLUTION		WHITE FLAKES		E
TRANSFORMER OIL		ASTM D-1040		G
TURPENTINE		DISTILLED SPIRIT		NR
ISOPROPYL ALCOHOL			10	E
ETHYL ALCOHOL			10	E
LEGEND: NR - NOT RECOMMENDED E - EXCELLENT G - GOOD F - FAIR				
<small>*THIS INFORMATION IS BASED ON TESTS PERFORMED ON SMALL UNSTRESSED SAMPLES. THE ACTUAL PERFORMANCE OF THE ARTICLE WILL DEPEND ON THE PRESENCE OF INTERNAL AND EXTERNAL STRESSED AND ORIENTATION IN THE MANUFACTURED ARTICLE</small>				

COMBUSTIBILITY

Like many other synthetic and natural building materials, OPTIX-L continuous cast acrylic sheet is combustible. The sheet should not be used in applications where codes or common sense would deem it unsafe. Data on small scale tests are available however, these tests are not intended to reflect hazards presented by this or any other material under actual fire conditions.

THICKNESS SELECTION

See Table VII for recommended minimum sheet thicknesses which are based on deflection, wind load, design and normal rabbet and channel depths.

TABLE VII MAJOR PANE DIMENSIONS VS. MINIMUM THICKNESS	
PANE SIZE MAJOR DIMENSIONS (IN.)	MINIMUM THICKNESS (IN.)
40	0.118"
63	0.177"
96	0.236"

TABLE VIII THICKNESS VS. CALIPER VARIATION		
THICKNESS (IN.)	VARIATION	
	MAX.	MIN.
0.118"	0.130	.0106
0.177"	0.195	0.159
0.220"	0.242	0.198
0.236"	0.260	0.212

WEATHERABILITY

OPTIX-L continuous cast acrylic sheet is outstanding in its ability to withstand continuous exposure to sun and UV radiation. No other type of plastic sheet offers such outstanding clarity, strength, and light transmittance in combination with long-term outdoor performance.

OPTICS

OPTIX-L continuous cast acrylic sheet has exceptional thickness tolerance control. This property (see Table VIII) ensures consistent quality and very low optical distortion. In addition, clear OPTIX-L has shown to provide 92-93% light transmittance, compared to 89% light transmittance of plate glass.

THERMAL PROPERTIES

OPTIX-L continuous cast acrylic sheet is a better thermal insulator than glass. The rate of heat transfer through glass ("K" factor) is four (4) times greater than that through OPTIX-L. The overall transmission coefficient or "U" factor for OPTIX-L Acrylic Sheet will be better than glass (see Table IX).

TABLE IX U-FACTOR FOR VERTICAL WINDOWS (BTU/HR. SQ. FT./°F)							
SHEET THICKNESS	WINTER HEAT LOSS			SHEET THICKNESS	SUMMER HEAT GAIN		
	1/8"	3/16"	1/4"		1/8"	3/16"	1/4"
SINGLE GLAZED	1.06	1.03	0.96	SINGLE GLAZED	0.98	0.93	0.89
DOUBLE GLAZED 1/4" AIR SPACE	0.55	0.52	0.49	DOUBLE GLAZED 1/4" AIR SPACE	0.56	0.53	0.50
DOUBLE GLAZED 1/2" AIR SPACE	0.47	0.45	0.43	DOUBLE GLAZED 1/2" AIR SPACE	0.50	0.48	0.45

Data apply to square and rectangular panes of OPTIX-L continuous cast acrylic sheet when the length is no more than three times the width. All edges continuously held. Sheet thickness selection is based on total deflection under uniform load limited to five percent of the short side, or three inches, whichever is smaller.


WEIGHT

OPTIX-L continuous cast acrylic sheet is considerably lighter than glass (50%) and aluminum (43%). See Table X.

TABLE X WEIGHT OF OPTIX-L CONTINUOUS CAST ACRYLIC SHEET			
THICKNESS (IN.)	CALCULATED (LB./SQ. FT)		
	ACRYLIC	GLASS	ALUMINUM
0.118	0.73	1.46	1.70
0.177	1.10	2.20	2.56
0.236	1.45	2.90	3.37

LIGHT TRANSMITTANCE

As seen in Figure 4, clear OPTIX-L continuous cast acrylic sheet has a high percentage of energy transmittance over the wavelengths where radiant power of the sun's energy is greatest.

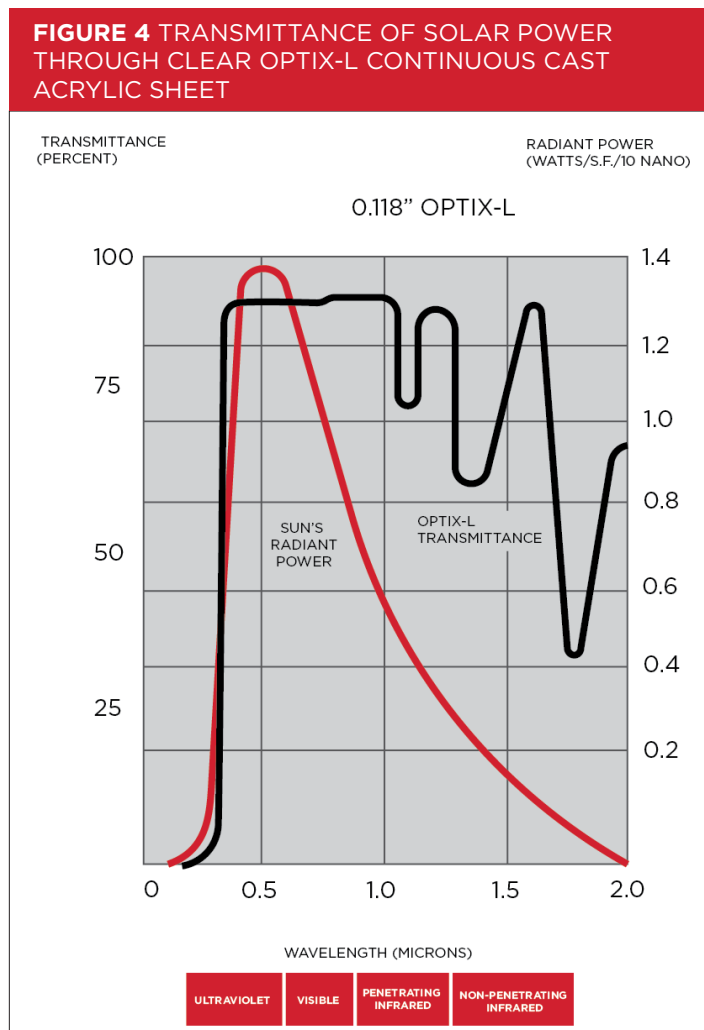

BREAKAGE RESISTANCE

OPTIX-L continuous cast acrylic sheet has significantly higher breakage resistance compared to traditional glazing materials. Table XI shows the impact performance of the sheet as a function of thickness.

TABLE XI BREAKAGE RESISTANCE AS A FUNCTION OF SHEET THICKNESS 5.0 LB POINTED DART OF 12" X 12" OPTIX-L ACRYLIC SHEET		
NORMAL THICKNESS (IN.)	MAX. DROP HEIGHT (IN.)	RELATIVE BREAK RESISTANCE
0.118	7.5	1
0.236	42.4	6

THERMOFORMABILITY

OPTIX-L continuous cast acrylic sheet can be readily thermoformed into almost an unlimited variety of forms and contours. Skylights, domes, and other decorative shapes can be easily obtained when sheet is heated to forming temperature. Moderate contours are often desirable and can be easily obtained without heating the sheet. OPTIX-L can be snapped into curved channel supports provided the radius of curvature is in excess of 250 times the thickness of the sheet.

CODE AND SPECIFICATIONS COMPLIANCE FEDERAL SPECIFICATIONS

Clear OPTIX-L continuous cast acrylic sheet meets or exceeds the properties and quality control provisions of Federal Specifications L-P-391D; OPTIX-L meets Type I (general purpose material having UV light absorbing properties.)

AMERICAN NATIONAL STANDARDS INSTITUTE

OPTIX-L continuous cast acrylic sheet complies with ANSI Z97.1 architectural glazing standard. Because of variations in local building codes, it is difficult to generalize on compliance of OPTIX-L for all applications. However, specific building code information can be supplied on request.

OTHER

OPTIX-L complies with Consumer Product Safety Commission safety standard CPSC 16 CFR 1201 for architectural glazing, and can be used in Category I and Category II products. Clear OPTIX-L Acrylic Sheet meets the requirements of ASTM D4802 - A-2, Finish 1.

CARE AND CLEANING

OPTIX-L continuous cast acrylic sheet has a highly polished lustrous surface and will retain its appearance for many years if given proper care. Cleansing materials containing abrasives such as scouring powders or strong solvents as found in some window cleaning preparations should never be used to clean the sheet. Gasoline, acetone, chlorinated solvents, or denatured alcohol tend to soften the surface of the plastic and often cause crazing.

When first installed, glazing compound and paper masking adhesive can be easily removed with hexane, naphtha, kerosene or isopropanol. These solvents are flammable. While using them, avoid sparks, open flame or other ignition sources, and do not smoke. They may be applied with a soft absorbent cloth, followed by rinsing with clean water. Remaining drops of water should be wiped away with a soft chamois or moist cellulose sponge.

Thereafter, an occasional washing with mild soap or detergent and water solution is sufficient to keep OPTIX-L continuous cast acrylic sheet looking like new. Household ammonia in water in the concentrations recommended for general cleaning is also excellent.

Fine hair scratches may be removed or minimized with a mild automobile cleaner polish. Cleaner polish has a very mild abrasive action and its wax content tends to fill small scratches and make them less visible.

DISTRIBUTION

OPTIX-L continuous cast acrylic sheet is available nationwide through plastics distributors. For information on sizes and availability, please contact your local authorized distributor or PLASKOLITE.

DESIGN AND FABRICATION SOLAR COLLECTORS

GENERAL

OPTIX-L continuous cast acrylic sheet is an excellent outer glazing material for all types of solar collectors operating at 180°F or below. Because of its chemical structure, acrylic sheet is inherently resistant to discoloration and loss of light transmission during extended exposure to weather.

In this respect, OPTIX-L continuous cast acrylic sheet is unsurpassed by any other class of transparent plastics.

Compared with glass, OPTIX-L continuous cast acrylic sheet offers advantages in solar transmission, weight reduction, impact resistance and on-site fabrication. In addition, where curved or vaulted collector covers are desired, flat OPTIX-L can be simply inserted into a curved retaining channel thus avoiding bulky, preformed covers with other materials such as Teflon® FEP 100A film to achieve outstanding collector insulation efficiency.

LIGHT TRANSMITTANCE

OPTIX-L continuous cast acrylic sheet allows a high percentage of energy transmittance over the wavelengths where radiant power of the sun's energy is greatest.

In addition, reports indicate that OPTIX-L sheet performs better than glass in its ability to trap infrared (IR) from hot solar collector plates.

FORMING AND FABRICATION

OPTIX-L continuous cast acrylic sheet can be formed easily and inexpensively into an almost endless variety of configurations. It is frequently possible to take advantage of this forming ease to provide lowered unit cost and weight.

Common wood or metal-working tools can be used to fabricate the sheet. Circular saws, band saws, drills, routers, lasers, etc., can be successfully employed in shaping sheet contours. Bits and blades should, however, be kept sharp and feed should be slow and continuous to avoid chipping.


*Teflon® is a registered trademark of Dupont

COLLECTOR DESIGN

OPTIX-L continuous cast acrylic sheet can be used with a wide variety of collector designs. Units employing flat glazing are probably the simplest. Covers designed in a slight vault configuration provide improved load bearing characteristics.

Because of the outstanding weatherability and fabrication ease, the sheet can be used for the collector cover and case.

Schematic illustration of these designs with OPTIX-L continuous cast acrylic sheet are shown below:

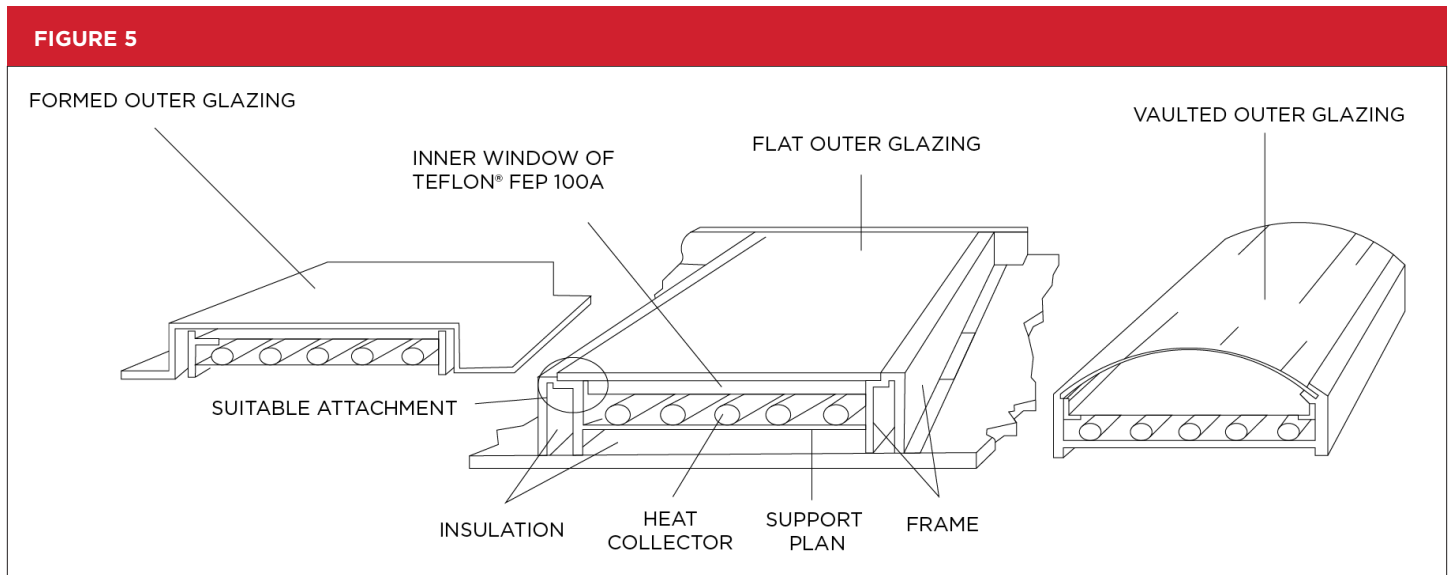

STRIP HEAT BENDING AND COLD FORMING

BENDING

Simple straight line bends which are relatively short (up to 24" in.) can be easily and readily achieved in OPTIX-L continuous cast acrylic sheet by heating only the narrow area that needs to be formed. There is no need to heat the entire sheet in an oven when only simple angles are required. Because the piece stays cold, except for the narrow heated area in the center, both sides of the angle will remain flat and distortion-free. Bowing can, however, result from uneven heating and cooling. In addition, pieces longer than 24" in. may have a tendency to bow.


To prevent distortion or damage to the sheet surface, OPTIX-L continuous cast acrylic sheet should be kept at least 1/16" in. away from the hot tube. When using a flexible strip heater, the sheet may be placed on the heater but care must be taken to avoid overheating and marking the sheet.

For heating at a faster rate or for forming sheet over 0.250" in. thick, strip heaters should be placed on both sides of the sheet.

The masking must be removed in the bend area only, so the remainder of the part is protected from marks and scratches.

Sharper, straighter right angle bends can be achieved by machining a 90° groove along the inside of the bend line before heating. After bending, the groove can be sealed by capillary cementing. (See Figure 6)

FIGURE 6: STRAIGHT LINE BEND

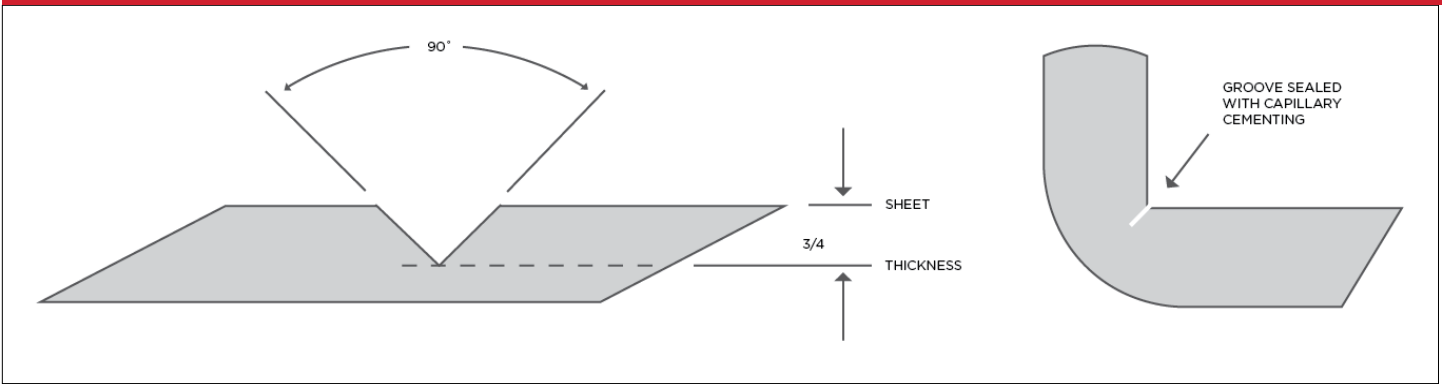

COLD FORMING

Unheated OPTIX-L continuous cast acrylic sheet can be bent into a curved frame provided the curve has a radius of at least 180 times the thickness of the sheet. Sharper bending of unheated OPTIX-L may result in stress crazing.

OPTIX-L THICKNESS	MINIMUM RADIUS OF CURVATURE	EQUAL TO CIRCLE OF
0.090"	17"	34" Dia.
0.118"	22"	44" Dia.
0.177"	33"	66" Dia.
0.236"	45"	90" Dia.

LAYOUT

Cutting lines may be penciled directly on paper replacement masking or may be marked on the surface of unmasked acrylic sheets with a china-marking pencil. If the acrylic sheet is to be heated, the china markings must be removed because the wax can melt and dye the sheet. Patterns can be traced directly on the acrylic sheet with a pencil and carbon paper.

For close tolerances, a cutting scribe or razor blade can be used to outline the work directly on the surface of the sheet. When many identical pieces are to be cut out, templates made of plastic, wood or metal are useful for guiding the scribe. Masking should be removed from the surface before scribing and then replaced 0.250" in. (0.635 cm) from the scribed markings prior to cutting. Naturally, fabricators can take full advantage of CNC routers and laser units to ensure the highest productivity on repetitive shapes.

CUTTING

The choice of cutting equipment depends on the type of work to be done. For example, circular saws can be used for making long, straight cuts through acrylic sheets of all thicknesses. Band saws can be used for cutting large radius curves and for straight cuts. Jigsaws can be used for light work and for cutting curves of small radii. Generally, the cutting speed should be faster as the acrylic sheet gets thinner.

Cutting blades must be kept clean and sharp. A blade in continual use often accumulates a residue which may cause chipping, binding and a whipping action during sawing. Cutting blades should be cleaned at the end of each day or at the end of each long run. Strong solvents for acrylic resins such as acetone or toluene can be used to clean the blades. Cutting blades and mandrels should always be kept free of any play or wobble.

The use of a lubricant, such as soap and water, mineral oil, or a compatible cutting fluid will help to dissipate frictional heat, extend blade life, and reduce the tendency of the acrylic to gum up along the blade edge. The application of masking tape over the area to be cut will reduce the tendency for the edge of acrylic sheet to chip during cutting. Colored acrylic sheet which contains slightly abrasive pigments will dull cutting blades faster than clear acrylic sheet.

STRAIGHT LINE CUTTING AND CIRCULAR SAWS

Circular saws used to cut OPTIX-L continuous cast acrylic sheet should be hollow-ground to aid cooling and to prevent binding. Expansion slots should be present in the rim of the saw to prevent heat warping and whipping of the blade. Carbide-tipped blades will produce a superior cut and provide a longer life between sharpenings than steel blades. Circular saws should be run at relatively high speeds of 8000 - 12000 linear feet per minute (2440 - 3660 m/min.).

OPTIX-L continuous cast acrylic sheet should be fed slowly enough to prevent overheating by friction with the blade. The use of a lubricant or a coolant will permit the plastic to be cut at a faster rate without over-heating. A lubricant will also reduce the danger of chipping, produce cleaner cuts, help overcome the tendency of the saw blade to bind or stick, extend the life of the saw blade, and reduce the amount of "smoking". Water is a satisfactory lubricant for cutting acrylic sheet. If equipment corrosion is a factor, water soluble oil can be used as a coolant. Bar soap may also be employed as a lubricant. When several pieces are cut simultaneously, oiled paper may be placed between the sheets of plastic to supply lubrication. Table XII can serve as a guide in selecting the proper circular saw blade to cut the sheet.

TABLE XII CIRCULAR SAW BLADE SELECTION TABLE				
SHEET THICKNESS IN.	BLADE THICKNESS		TEETH PER	
	(MM)	IN.	(MM)	IN.
0.040-0.080	(1-2.0)	1/16	(1.6)	8-14
0.080-0.150	(2.0-3.8)	3/32	(2.4)	6-8
0.150-0.375	(3.8-9.5)	3/32	(2.4)	5-6
0.375-0.750	(9.5-19.0)	1/8	(3.2)	3-4
0.750-4.000	(19.0-101.6)	5/32	(4.0)	3-3.5

All saw teeth should have a uniform height, the same shape, a uniform hook or “rake” between 0° and 5° to avoid chipping, and a slight set to give clearance of 0.010” in to 0.015” in. (0.254 mm to 0.375 mm). An 8-inch (20.3 cm) diameter blade is suggested for lighter work, while a 12-inch (30.5 cm) diameter heavy gauge blade should be used for heavier work. A large diameter blade provides a greater cooling surface and a thicker blade will conduct away more surface frictional heat.

The circular saw blade should be set at a height slightly greater than the thickness of the section to be cut. The acrylic piece should be held firmly and placed in a straight line parallel with the saw blade to prevent chipping. A separator blade directly behind the saw blade can be used to prevent the kerf from closing in on or reknitting the edge. Using a sliding jig to provide an even and steady feed of the acrylic sheets will result in smoother cuts and longer blade life.

IMPORTANT: As the blade is entering or leaving the cut acrylic piece, the feed rate should be reduced to avoid chipping at the corners.

When cutting masked sheet, the adhesive can build up between adjacent teeth of the saw blade. This gumming of the blade can be reduced by applying a small amount of lubricant to the blade.

Traveling saws are suggested for cutting stacks of acrylic sheet or for making straight cuts longer than three (3) feet. The plastic remains stationary, positioned with a hold-down bar to prevent chattering, while the saw is power-driven or is hand-cranked through the acrylic sheet at a rate of 10-25 ft./min. (3-7.6 m/min.). A traveling saw is also desirable for cutting unmasked acrylic sheets since the unprotected surfaces do not slide across a saw table.

CURVED LINE CUTTING WITH BAND SAWS

Band saws are useful for cutting curves in flat acrylic sheets, for trimming formed parts, and for cutting thick sections or stacked acrylic sheets. Variable speed band saws, which can run at 5000 ft. /min. (1524 m/ min.), and have a 28” to 36” in. (71 to 91 cm) throat, are best suited for production work. (4500 ft./min.) for material 1/16” to 1/8” in. 0.16 to 0.32 cm thick, about 3750 ft./min. 1143m/min. for material 1/8” to 1” in. 0.32 cm to 2.54 cm thick, and about 3000 ft./min. 915 m/min for material thicker than 1 inch 2.54 cm.

Fine teeth with no set will produce a smooth cut if the work is fed slowly. Generally, tooth size should be larger with the increasing thickness of the acrylic sheet.

Metal-cutting blades are generally the best type for cutting acrylic sheet. The selection of the blade width and thickness, and the number of teeth, depends on the radius and the thickness of the acrylic sheet to be cut. Table XIII can serve as a guide for selection of a band saw blade.

TABLE XIII BAND SAW BLADE SELECTION TABLE						
MINIMUM RADIUS TO BE CUT IN. (CM)		BLADE WIDTH IN. (CM)		BLADE THICKNESS IN. (CM)		TEETH PER INCH
1/2	1.27	3/16	0.5	0.028	0.7	7
3/4	1.90	1/4	0.64	0.028	0.7	7
1 ¹ / ₇	3.8	3/8	0.95	0.028	0.7	6
2 ¹ / ₄	5.7	1/2	1.27	0.032	0.8	5
3	7.6	5/8	1.59	0.032	0.8	5
4 ¹ / ₂	11.4	3/4	1.90	0.032	0.8	4
8	20.4	1	2.54	0.035	0.9	4
12	30.5	1 ¹ / ₃	3.18	0.035	0.9	3
20	50.8	1 ¹ / ₂	3.8	0.035	0.9	3

Suitable saw guides should be adjusted close to the work, since any blade weaving or whipping will create additional frictional heat, and cause a ragged cut. The acrylic sheets must be kept in continuous motion and the feed pressure must be applied evenly to minimize gumming tendencies and prevent the blade from binding and breaking. The cutting blade should always enter and leave the acrylic sheet slowly to prevent chipping at the corners. As with circular saw blades, band saws must be periodically cleaned with a solvent which will remove the gum accumulation.

TIGHT CUTTING WITH JIGSAWS

Jigsaws should be used for small-diameter curves and for interior cuts in acrylic sheet. The blades are narrow and can easily be inserted through a drilled hole. The jigsaw blades should be the metal-cutting type. Saw guides should be adjusted as close to the work as possible to minimize the weave of the blade.

Because the working stroke is short, frictional heat can build up quickly during cutting. Often all of the chips do not clear the blade, which can result in gumming. To prevent the acrylic sheet from overheating and gumming, and the fresh cut from reknitting, the feed must be slow and steady. Jigsaws with integral blowers are useful to remove sawdust from the work.

OTHER SAWS AND CUTTING DEVICES

Portable, high-speed circular saws are useful for trimming large formed parts of acrylic where it is more convenient to bring the tool to the work than the work to the tool. Extreme care must be exercised. The tool must be well balanced and run without vibration. The acrylic part to be trimmed should be secured in a jig and well supported.

HOLE-CUTTING

Tubular blades mounted in a drill press are convenient for cutting large round holes in OPTIX-L continuous cast acrylic sheet.

SCORE-CUTTING

The same method of scoring and breaking used for cutting glass can be used for straight-cutting acrylic sheets. A simple holding device to provide both an edge over which to break the scored acrylic sheet and a means of applying a uniform bending pressure can be used. In general, the thicker the acrylic sheet to be cut, the deeper the score should be made.

ROUTING

Wood shavers or routers can be used to cut edges and slots of various shapes into pieces of acrylic sheet. The type of cutter used is determined by the desired shape of the cut.

In general, the greater the speed of the router, the fewer the cutting edges required to produce a clean, smooth cut. For example, square routing templates can best be accomplished with six- to ten-bladed cutters operating at speeds of 2000 to 5000 ft. /min. (608 to 1525m/min.). Cutters with only two or three cutting edges and 2"-3" in. (5.08-7.62 cm) in diameter would require speeds of 5000 to 9000 ft. /min. (1524 to 2744 m/min.) for acceptable routing of acrylic sheet.

Blades should be kept sharp. The cutter should be ground with a back clearance of about 10°, and rake angle between 0° and 15°. For rabbet or step routes in acrylic sheet, the cutting teeth should be backed off on the underside to avoid drag and burn marks. Whenever possible, the corners of the routing cutters should be ground to a slight radius in order to produce a fillet at the bottom of the rout. The elimination of sharp corners prevents the concentration of stresses where failure of an acrylic part can result.

OPTIX-L continuous cast acrylic sheet should be fed slowly and continuously. A suction system or an air blast will remove chips and help cool the cutter. Portable hand routers are useful for trimming edges of acrylic sheets and for surface routing of intricate designs.

LASER

GENERAL

CO₂ laser systems provide an ideal, non-contact method for cutting and engraving of OPTIX-L continuous cast acrylic sheet. Both processes can be combined into a single manufacturing step, and run without the need for tool cleaning or sharpening and without cutting fluids or polishing compounds.

The 10.6-micron wavelength emitted from the CO₂ laser is absorbed very efficiently by polymeric materials such as OPTIX-L continuous cast acrylic sheet. The absorbed laser light is converted to heat, and the heat causes material, that is directly in the laser's path, to vaporize (ablation). Higher laser power densities can be used to cut through OPTIX-L leaving a clean, square and polished edge. Lower laser power densities can be used to engrave a high definition, permanent mark into the surface of the material for branding or serializing parts.

LASER CUTTING

A 2.0 lens (two inch focal length) is suitable for most cutting applications. Air assist with back sweep is recommended for cuts greater than 0.250" in. The back sweep will allow direction of the high pressure air across the surface of the work piece instead of down the cut where it could cause frosting of the cut edge. Gas assist with nitrogen is recommended for thicknesses greater than 0.500" in. For gas assist, a cone will provide better direction of the low pressure nitrogen to the cut. Since the nitrogen pressure is low, frosting of the edge due to rapid cooling is not an issue. Also, for thicknesses greater than 0.500" in., switching to a 3.0 lens will provide a more uniform cut through the thickness of the work piece due to reduced beam divergence.

When cutting, it is best to remove the masking from the top side of the work piece so that it will not interfere with the laser cut. Leave the masking on the bottom side of the piece to protect it from reflections off the cutting table. For applications where edge quality is critical, the part should be elevated about an inch above the cutting table to avoid all reflections.

For cutting, the laser is usually run at 100% of its rated power. Lower cut speeds are used for thicker materials. Figure 7 provides guidance on laser power selection and laser cutting speed respectively.

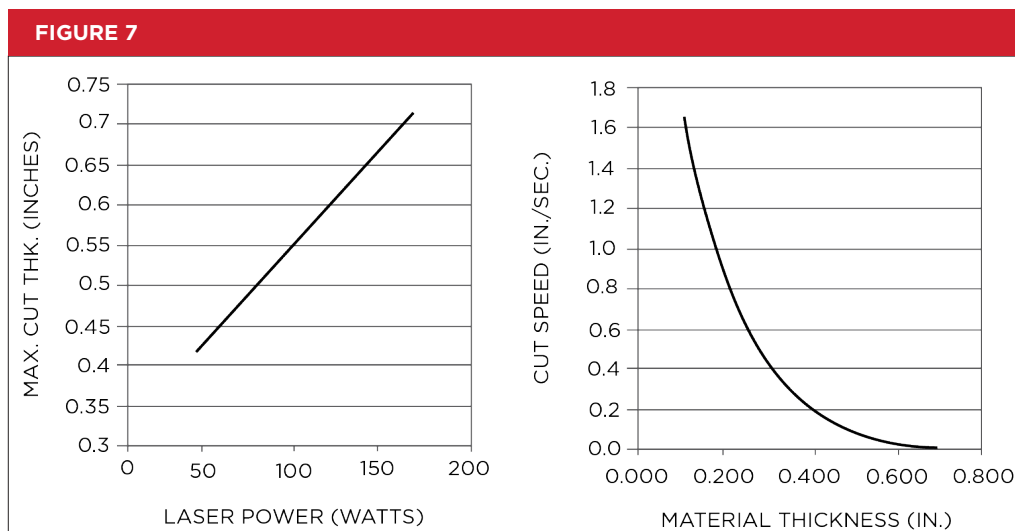


Figure 7. Maximum thickness that can be cut as a function of laser power (left), and maximum cut speed as a function of material thickness (right).

LASER ENGRAVING

Laser engraving can be done in raster mode as well as vector mode. In each case, the engraving depth is a function of the laser power density. Figure 8 provides information on raster engraving depth and vector engraving depth as a function of laser power at constant engraving speed.

A 2.0 lens (two inch focal length) is suitable for most laser engraving applications. For applications that require very fine detail, High Power Density Focusing Optics (HPDFO) is recommended. This will provide a much smaller laser spot size than the 2.0 lens.

For most applications, the masking should be removed from the top side of the work piece. The top side masking should be left in place for deep raster engraving (depths of greater than 0.010") in order to avoid hazing of adjacent surfaces due to re-deposition of ablated material. Leave the masking on the bottom side of the part to protect it from mechanical damage (scratches).

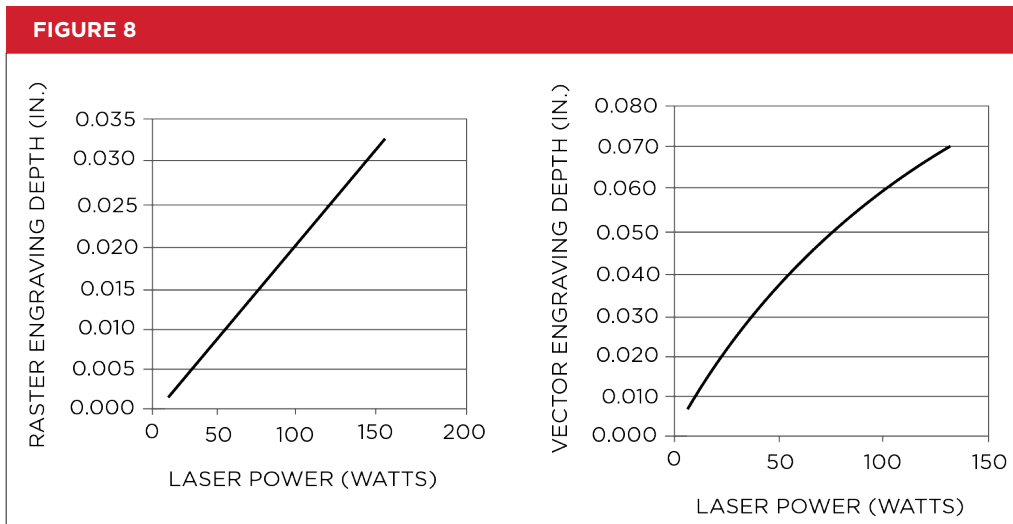


Figure 8. Raster engraving depth as a function of laser power (left), and vector engraving depth as a function of laser power (right).

HIGH VOLUME MANUFACTURING


For cutting operations, increasing the laser power will improve the throughput of the laser system. A dual laser system allows the beams from two lasers to be combined into a single beam, thus providing the maximum cutting power. For engraving, the two beams can be operated in parallel so that two identical parts can be processed simultaneously. Work surfaces as small as 16" x 12" in. are available for smaller work pieces, and sizes range up to 48" x 24" in. for larger work pieces. Options are also available for longer work pieces (i.e. 24" in. x unlimited length).

CAUTION: Acrylic materials such as OPTIX-L continuous cast acrylic sheet are flammable. Laser systems should not be left unattended when processing any acrylic material.

DRILLING

Both sides of the acrylic sheet being drilled should be firmly supported using a specially designed jig or by clamping to wood. This will minimize chipping.

Standard vertical-spindle drill presses, as well as portable hand drills, may be used for drilling acrylic sheet. Twist drills can be used if their cutting edges are “dubbed off” to a zero degree rake angle. Standard metal drills will pull and grab the acrylic sheet unless the cutting edge is “dubbed off” to a zero degree rake angle. Standard drills will perform well with acrylic sheet if they are modified to the following specifications (see Figure 9):

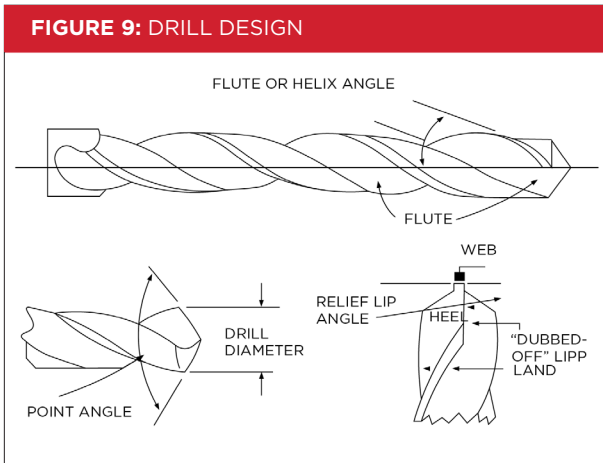

FLUTE OR HELIX ANGLE: 17°

POINT ANGLE: 70°-120° (ANGLE DEPENDS ON PART THICKNESS)

LIP CLEARANCE OR RELIEF ANGLE: 4°-8°

POLISHED LANDS: ONE- QUARTER THE WIDTH OF THE HEEL

Deep and polished flutes facilitate the removal of chips. Nicks or scratches on the drill will mar the surface of the hole. If the proper drill, drill speed, and feed rate are being used, continuous spiral chips or ribbons will form. For larger diameter drills, slower rotating speeds will give the best results.

Drill lubricants aid in chip removal, carry away heat, and improve surface finish of a hole. Good lubricants for drilling acrylic parts are a soap-in-water solution of mineral oil. The use of mineral oil alone will require an extra cleaning operation. In some cases, add one (1) part of mineral oil to as much as ten (10) parts of soap-in-water solution. In drilling deep holes, it is desirable to immerse the part in the coolant lubricant. A steady stream of lubricant directed at the drill may also be used if the drill is withdrawn about every 0.5” in. (1.27 cm) to allow the chips to be cleared and the hole to be filled with lubricant. Compressed air can often be used as a coolant for holes with a depth-to-diameter ratio of less than 5 to 1. Shallow holes can usually be drilled into acrylic sheet without a lubricant if care is exercised to avoid overheating.

Whole saws and fly cutters are useful for cutting holes greater than 1” in. (2.54 cm) in diameter. A modified long-lead twist drill with a sharp lip is particularly useful for drilling thin sheets of acrylic.

THREADING AND TAPPING

It is possible to thread or tap OPTIX-L continuous cast acrylic sheet satisfactorily with standard thread forms. The following recommendations should be followed.

Such thread as the United States Standard (American Coarse Thread Series), Whitworth Standard (British Standard Series), and Acme are generally satisfactory. Sharp “V” threads are to be avoided due to the ease with which the apex fractures. Coarse pitch threads are preferred because of their added strength.

When threading or tapping OPTIX-L continuous cast acrylic sheet to fit a metal bolt or nut, allowance should be made for the different thermal expansion coefficients of the two materials. A slight increase over normal metal clearance is usually ample. In addition, when a number of bolt holes are drilled in line, the holes should be elongated to allow for lateral movement resulting from temperature changes.

If service temperature variations are expected to be extreme, dimensional changes will be too great and threading is not recommended. Also, where the internal threads may be subjected to excessive shock or torque-loading, or where it may be necessary to remove and reinsert the bolt frequently with the potential for wear or cross-threading, threaded metal inserts or fittings should be used. Such components can be inserted into the acrylic piece by ultrasonic welding.

Either hand or machine methods may be employed for threading or tapping OPTIX-L continuous cast acrylic sheet. The material also can work well in lathes or automatic screw machines. Standard taps and dies should be operated at 25% slower speed than used for brass. Higher speeds cause excessive frictional heat and gumming of the chips. Taps should be backed out frequently to clear chips and avoid jamming.

In hand-tapping small holes (0.200” in. or less) it may not be necessary to use a lubricant if care is exercised. On larger holes, a lubricant such as mineral oil is recommended for drilling. For machine-tapping or threading, the work should be flooded with the proper lubricant.


BLANKING AND PUNCHING

OPTIX-L continuous cast acrylic sheets which have been heated may be cut or blanked with steel rule or open-faced dies. The thicker the acrylic sheet, the longer the heating time. Overheating of the acrylic sheet will cause edge “drag” by the die to give irregular, concave edges.



CEMENTING

OPTIX-L continuous cast acrylic sheets can be fastened to other materials by mechanical means or with cements or adhesives. Some typical methods of joining together acrylic sheets are illustrated in Figure 10.

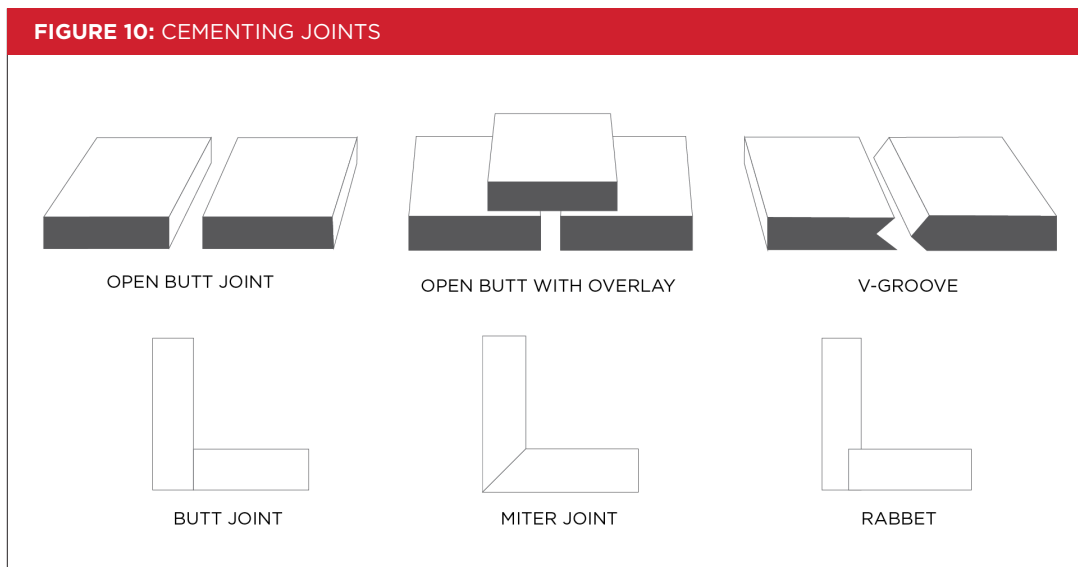

For large area constructions, as in glazing which would involve the joining of many acrylic sheets, the use of formed flanges or extruded channels will provide a strong construction and joints of low visibility. Gaskets are sometimes used with this method of assembly.

Acrylic sheet can be bonded together with strong, transparent joints. Strength, appearance and performance of a cemented joint depends on the elimination of internal stresses, the proper preparation of the mating surfaces, the choice of a proper cement or adhesive, and the use of good technique.

SAFETY PRECAUTIONS

Many types of cement used for bonding acrylic sheets are toxic if ingested or inhaled for extended periods, and can irritate the skin after repeated contact. Some of the cements are flammable. When working with them, adequate ventilation should always be provided, and contact with the skin, eyes, and clothing should be avoided. Recommended procedures and precautions of cement manufacturers should be considered as minimum requirements.

PREVENTION OF INTERNAL STRESS

Thermoforming or machining operations will sometimes produce internal stress in acrylic parts or sheet. Excessive stress in acrylic makes the surface susceptible to crazing by some cements. Internal stress can be avoided by the proper choice of processing, thermoforming, or machining conditions. Some of these internal stresses can be relieved by annealing (discussed later in this guide).

SURFACE PREPARATION AND FITTING

Surfaces to be joined should be clean and fit together as matching flat surfaces. The edges of the two acrylic parts to be cemented should never be polished as this tends to round the corners and decrease the contact area of the joint.

CEMENTING ACRYLICS TO ACRYLICS

OPTIX-L continuous cast acrylic sheet can be joined or bonded together with several general types of commercially available cements or adhesives. They are the solvent, polymer-solvent and polymerizable types. See Table XIV.

Solvent-type cements are the easiest, most economical and convenient types to use. The solvent softens the mating surfaces so that complete fusion can be achieved at the interface of the joint's surfaces. The joint then hardens as the solvent diffuses and evaporates. Ordinarily, the joints require no post-treatment. Solvent cements are best applied at temperatures above 75°F (24°C). Lower temperatures slow the cure process.

TABLE XIV CEMENT FOR BONDING ACRYLIC	
TYPE	SOURCE*
<u>SOLVENT TYPE</u> WELD-ON 3 SC 94	IPS CORP (800.421.2677, IPSCORP.COM) CASEWAY INDUSTRIAL PRODUCTS (989/391/9992, CASEWAYPRODCUTS.COM)
<u>MIXED SOLVENT TYPE</u> WELD-ON 4	IPS
<u>POLYMER-SOLVENT TYPE</u> WELD-ON 16	IPS
<u>POLYMERIZABLE TYPE</u> WELD-ON 10 WELD-ON 40 PS-30	IPS CASEWAY INDUSTRIAL PRODUCTS (989/391/9992, CASEWAYPRODCUTS.COM)
*NOTE: OTHER BONDING CEMENTS ARE AVAILABLE FROM MANY PLASTICS DISTRIBUTORS AND CHEMICAL SUPPLY HOUSES.	

Lower temperatures also slow down the solvent action on the acrylic resin. Conditions of high relative humidity can produce cloudy joints due to the condensation of moisture from the air onto the area of the joint cooled by the evaporating solvent.

Types of solvent cement which generally provide bonds with greater strength and are not subject to weather problems are mixtures of lower and higher boiling solvents such as methyl methacrylate monomer, acetic acid and a fast evaporating solvent.

Some solvent cement has been modified to make them useful on lower molecular weight melt processed acrylic sheet. These cements will not yield satisfactory bonds on high molecular weight sheet such as OPTIX-L continuous cast acrylic sheet. Be certain to select cement formulated for the type of sheet you wish to bond.

Polymer-solvent type cements, as the name implies, are a solvent in which acrylic polymer has been dissolved. This cement has advantages of the solvent-type cements. Since they are more viscous, they can be used where the surfaces to be joined are not smooth or do not fit together well. The polymer-solvent type cement may also be prepared by the fabricator. Dissolve acrylic chips or shavings in the solvent system of choice to obtain the viscosity which best suits the particular methods of cementing.

Polymerizable-type cements consist primarily of two components, methyl methacrylate monomer and a catalyst which serves to convert the monomer into polymer when the bond sets. The monomer usually has polymer dissolved in it to increase its viscosity, and improve the handling characteristics of the cement. An accelerator may also be added as a third ingredient to shorten the polymerization period.

Polymerizable cements give the advantage of fast initial set, and the cemented joints are usually sufficiently hard and strong for machining within four (4) hours after assembly. The main disadvantage is that once the components have been mixed, the polymerization reaction begins and continues until the cement is hardened. The cement generally remains in a useful condition for one-half hour to one hour after mixing. The life of the mixture may be extended by keeping the mixture cool.

Cyanoacrylate-based cements polymerize on application to the joint. However, the surfaces to be joined must be smooth and fit together perfectly if a good bond is to be achieved. These types of cements may not result in a cohesive bond.

CEMENTING TECHNIQUES FOR ACRYLIC TO ACRYLIC

When two pieces of acrylic sheet are to be cemented together, they should have similar molecular weight (i.e., produced by the same process). Otherwise, the faster dissolving, lower molecular weight portion will immobilize the solvent before the higher molecular weight portion is softened, and weak bonds or no bond will result.

Cements can be applied by dip, syringe or brush methods. The best method will depend on the type of cement and the type of joint being used. The preferred method for cement types is shown in Table XV.

TABLE XV PREFERRED CEMENTING TECHNIQUES	
CEMENT TYPES	CEMENTING TECHNIQUES
SOLVENT AND POLYMER-SOLVENT	DIP, SYRINGE, BRUSH, DROPPER
POLYMER-SOLVENT AND POLYMERIZABLE	BRUSH, DROPPER

The dip method can be used with solvent-type cements. The acrylic pieces to be cemented are dipped in the cement and soaked until the surface is suitably softened. After the soak period, the two acrylic parts should be rapidly assembled and the joint held gently together for about thirty (30) seconds before applying pressure.

The syringe method is sometimes used with solvent cements when the two mating acrylic surfaces are very well matched. The joint may be secured in a jig and the cement introduced to the edges of the joint with a hypodermic syringe or an eye dropper. The cement is allowed to spread throughout the joint area by capillary action.

If the cement is sufficiently viscous, it can be brushed on the surface to be bonded. The viscosity of solvent-type cements can be increased by dissolving them in chips or shavings of OPTIX-L continuous cast acrylic sheet. This is the polymer-solvent cement discussed earlier. The cement is then brushed on and allowed to soften the surface of the acrylic part sufficiently to permit the formation of a cohesive bond. The joint is then assembled and placed in a jig.

BONDING ACRYLICS TO OTHER MATERIALS

Strong bonds between acrylic sheet and metal, wood, other plastics, rubber and other substrates may be obtained with the proper cements. To compensate for differences in coefficients of thermal expansion between acrylic sheet and other materials, the selected cement should remain somewhat elastic and not harden on aging.

Where the coefficients of thermal expansion are reasonably similar, the polymerizing type cements may be used. The primary advantage of this type of cement is that the strength of the bond develops quickly and the parts can be removed from the fabrication fixture sooner than if adhesives are used.

When two different types of plastic are to be joined, solvent cements can be used. However, test joints must be made to evaluate the feasibility of using this procedure. Hot melt adhesives can also be used to bond acrylics to other plastics, wood and metals. The surface of the substrate should be thoroughly cleaned before cementing. For metals, the bond strength can often be increased by roughening the metal surface by sanding or sand blasting. For rubber, adhesion may be improved by applying sulfuric acid to the rubber surface until the surface hardens, then wash away the acid and flex the hardened rubber. This will cause the rubber surface to crack, and a rough area with minute cracks will result. For glass, hard set cements should be avoided since rigid bonds may cause the glass to shatter with slight changes in temperature. A list of cements and adhesives that have been used successfully to bond acrylic sheet and parts to various non-acrylic substrates is shown in Table XVI.

TABLE XVI CEMENTS FOR BONDING ACRYLIC TO OTHER MATERIALS			
OTHER MATERIAL	CEMENT & SOURCE	OTHER MATERIAL	CEMENT & SOURCE
METAL	'DOWSIL' 732 RTV DOW CORNING CORP. (dow.com)	OTHER PLASTICS	PS-18 AND PS-30 (casewayproducts.com)
	RESIWELD NO. 7004	PHENOLICS	PENACOLITE ADHESIVE G1124 (koppers.com)
	"CORPORATION" 506 (lord.com)	GLASS	SMOOTH-ON LORD 506 LORD CORPORATION (lord.com)
WOOD & RUBBER	PENACOLITE ADHESIVE PLIOBOND ADHESIVES ASHLAND CHEMICALS, INC. CONVINGTON, KY	TAPES FOR CEMENTING	SCOTCH 600 OR 670 TAPE 3M CORPORATION (3M.com)

ANNEALING

The roughness and solvent-craze resistance of internally stressed acrylic sheet can sometimes be improved by relieving the stress through annealing, which increases the strength of cemented joints. Acrylic sheets can be annealed by heating them in a forced-air oven below the temperature which will cause the part to distort. The annealing time depends on the temperature, thickness, and type of acrylic involved. In general, a longer time at lower temperatures is preferred to shorter times at higher temperatures.

Suggested starting points for determining annealing times are shown in Table XVII. Annealing temperatures will normally be in the range of 140° to 200°F (60° to 93°C).

After heating for the suggested time, the parts should be cooled slowly to at least 120°F (49°C).

TABLE XVII SUGGESTED ANNEALING TIMES		
ACRYLIC SHEET THICKNESS		ANNEALING TIME
INCHES	MIN	HOURS
0.125	3.2	2
0.250	6.4	4
0.500	12.7	6
1.000	25.4	8

To obtain maximum benefit from annealing, the parts should be:

- » Annealed after all fabrication has been completed.
- » Free of protective spray coatings or masking.
- » Annealed in a uniformly heated, forced-air oven rather than by immersion in hot liquid.
- » Cooled slowly to room temperature after annealing. (For example, some fabricators cycle their oven temperatures so that the annealed parts will cool slowly overnight in the oven.)

Properly designed parts of OPTIX-L continuous cast acrylic sheet usually contain very low stress levels. There is little advantage gained from annealing the OPTIX-L continuous cast sheet and may add extra handling.

MECHANICAL JOINING

The threading and tapping of acrylic sheet has been described. When bolting pieces together, a compressible gasket is desirable to avoid applying excessive stress to the threads.

If metal accessories are mounted on an acrylic part, a rubber or cork composition gasket should always be used to cushion the acrylic part from direct contact with the metal. Shoulder bolts and washers should be employed to avoid excessive pressure on the acrylic part. Countersunk or flathead screws should not be used to mount metal directly to acrylic. Holes should be oversized to allow for thermal expansion.

PAINTING AND DECORATING

OPTIX-L continuous cast acrylic sheet can be painted or lacquered by conventional brushing or spraying techniques. Recommendations for the type, preparation, and viscosity of paints, as well as the type and amount of thinner, best suited for acrylic are available from paint suppliers.

Special wet or dry paints for filling recessed areas have been formulated for acrylic sheet by several paint manufacturers who supply the sign industry.

A clean surface is necessary for proper adhesion of the paint to the acrylic surface. A soft sponge soaked with a water-detergent solution will remove dirt. Grease can be removed with a noncrazing solvent such as isopropyl alcohol or naphtha. After washing, any detergent or soap must be completely rinsed off the surface with clear water. The acrylic surface must then be allowed to dry completely. A moist surface at the time of painting can cause poor adhesion and deterioration of the paint.

Static charges on the acrylic sheet which cause uneven paint patterns can be avoided by wiping the surface with a sponge dampened with naphtha. Paint should never be applied over films of antistatic detergents.

Non-acrylic paints or freshly applied acrylic paints can be removed by soaking the painted acrylic sheet or part in a 15% solution of caustic soda, or trisodium phosphate or a solution of "Trialene" soap, then thoroughly rinsing the surface with water. These solutions have little tendency to attack or craze the acrylic surface. However, these caustic solutions will very quickly attack human skin, and caution must be exercised when using this method. The operator's hands should always be protected with rubber gloves and eye goggles should be worn at all times. Follow the manufacturer's directions for safe handling.

FINISHING

The cost of decorating a product prior to forming is usually far less than decorating a formed product. Flat acrylic sheet can often be predecorated prior to forming. The pattern or decoration applied to the flat acrylic sheet must be properly distorted so that the desired pattern is produced after the acrylic sheet has been formed. The grid and snap-back methods are two methods which have been successfully used to design properly distorted patterns on acrylic sheet.

OPTIX-L continuous cast acrylic sheet can be decorated by a combination of pre-silk screening and pre-printing followed by further decoration or painting of the formed article. For example, in decorating a sign formed or assembled from acrylic sheet, silk screening could be used to apply the solid colors to the sheet, printing could be used to apply the white colors or delicate shading to the sheet, and brush or roller painting could be used to finish the flat, even tops of formed letters.

Designs can be carved or engraved on the surface of acrylic sheet. Small electric hand grinders with flexible shafts similar to those used by dentists can be used. The grinders can be ground to a very sharp point since the actual carving is accomplished with the side of the grinder. The grinder should be made of high-speed steel in order to withstand the frictional heat created.

Colored and metallic coils can be hot-stamped onto the surface of acrylic sheet. This technique requires stamping tools which can be carefully regulated to give proper and consistent stamping temperatures and pressures.

The original high-gloss surface of the sheet can usually be restored through a series of finishing operations if scratched during machining.

Finishing normally involves an initial sanding operation, followed by buffing, and finally a polishing operation. During all these operations, heat must be avoided. The acrylic sheet should be kept in constant motion with a minimum of pressure against the finishing wheels. Air or water cooling devices can be used to reduce frictional heat.

SANDING

An acrylic part should not be sanded unless the surface imperfections are too deep to be removed by buffing. The finest grit sandpaper which can remove the deepest imperfections should be selected. Waterproof "wet-or-dry" sandpaper should be used. The waterproof sandpaper should be soaked in water before use and kept wet while sanding.

For hand sanding, the paper should be wrapped around a wooden block, and a wide enough area should be sanded to minimize the formation of a recessed sink or uneven area. Machine sanding of acrylic sheet can be done with many types of equipment. Belt and vibrator sanders are suitable for sanding flat surfaces.

Disc sanders work well for removing material from straight edges and outside curves. Drum sanders are suitable for grooved edges. Air-driven or electric hand sanders work well for sanding small areas of large pieces of acrylic sheet which are too awkward to manipulate around a fixed machine. In all cases, the use of cooling water between the acrylic surface and the sand paper is recommended. Water permits the use of finer sandpaper, produces a finer finish because of the decreased frictional heat, and retards clogging of the sanding belt or disc.

In general, sanding machines are run at slower speeds for acrylic sheet than for wood and metal. With adequate water cooling, sanding wheels, discs, drums and belts can operate at speeds up to 3000 surface feet per minute (915 m/min.). Sandpaper with a silicon carbide abrasive of grit size No. 180 to 240 can be used for pre-roughing and general-purpose jobs, and grit sizes No. 230 to 600 should be used for fine work.

ASHING

Ashing is a coarse buffing operation useful for removing rough spots and scratches that are left after sanding acrylic sheet. In some cases, an ashing operation can be used in place of the sanding. Moderately hard abrasive wheels made of stitched cotton or flannel are usually operated at speeds of 2000 to 2500 ft./min. (610 to 762 m/min.). Usually a slurry consisting of O or FFF4 pumice and water is used for ashing. The water in the slurry acts as a coolant, and care must be taken to prevent the buff from becoming dry. A dry wheel can produce drag marks and cause overheating of the acrylic surface.

POLISHING

Acrylic polishing is done with softer buffing wheels and less abrasive polishing compounds. Initial polishing can be done with cotton or Domet flannel stitched buffs and polishing compounds such as very fine aluminum oxide or cerium oxide combined with wax, tallow or grease binders. Finer polishing can be accomplished with a softer buffing wheel containing little or no stitching and where only tallow has been applied. Soft buffing wheels made of imitation chamois or bleached muslin can also be used. The hardness of these buffs is decreased by the use of spacers which are smaller discs of the same material as that used in the wheel. The spacers are mounted between the face plates of the wheel.

After sanding or ashing to remove scratches from the acrylic surface, a final coating of wax applied by hand with a pad of soft flannel will complete the finishing operation. To minimize the attraction of dust to the acrylic, an antistatic cleaner may be applied to the surface with a soft cloth.

Polishing the surfaces of acrylic parts with a flame generally is not recommended. This technique will usually leave the polished area in a highly stressed condition, which can cause future crazing or failure of the part. Flame polishing is sometimes used to finish the areas which are inaccessible to ordinary buffing methods. In these cases, an oxy-hydrogen flame should be used rather than an oxy-acetylene flame, which can deposit carbon on the surface. The nozzle, held at 4"-6" in. (10.2-15.2 cm) from the surface, should be moved across the plastic at the rate of approximately 4" in. (10.2 cm) per second. If the flame is moved too slowly, overheating, bubbling or ignition of the surface can occur. After the acrylic surface has cooled, a second application of the flame often will improve the surface. Flame polished parts should be annealed to relieve the stress.

The use of solvents to polish the surface or edges of acrylic is not recommended.

ANTISTATIC COATINGS

During handling, acrylic sheet can accumulate static charges which attract and cause accumulation of dust on the surface. These charges can be dissipated by wiping the surface with a water-dampened cloth. Static charges can be removed from surfaces to be painted by wiping the acrylic sheet with a clean, soft cloth slightly damp with a light grade of naphtha. Many commercially available antistatic sprays work well with acrylic parts, but should not be used for surfaces to be painted.

PLASKOLITE

A GLOBAL LEADER IN THE PRODUCTION OF THERMOPLASTIC SHEET

FOUNDED IN 1950

Our Mission: to deliver superior thermoplastic sheet, coatings and polymers to the world, through long-lasting customer relationships and hands-on customer service.

MANUFACTURING LOCATIONS



From our founding, PLASKOLITE strives to treat our employees, our customers, our community and the world, with kindness, dignity and respect. This drives our continuing effort to create sustainable products, in a sustainable manner, for future generations. This on-going commitment is expressed in the

PLASKOLITE Sustainable Ecosystem:

QUICK FACTS

STATUS: Privately held


GLOBAL HEADQUARTERS: Columbus, OH

EMPLOYEES: 1900 Worldwide

MARKETS SERVED: Signage, Lighting, Retail Display, Construction, Transportation, Security, Bath & Spa, Industrial, Architecture, Green Houses

OUR PILLARS OF SUSTAINABILITY

EACH CONTRIBUTES TO MAKING THE WORLD A BETTER PLACE

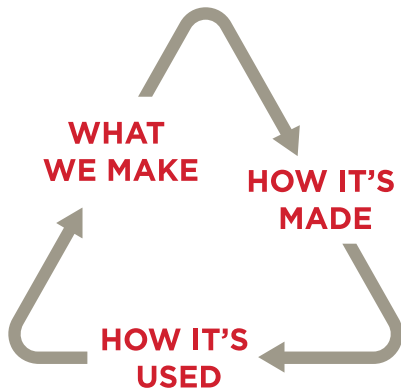

WHAT WE MAKE

Versatile, high-quality, durable thermoplastic materials...not single-use plastics

HOW IT'S MADE

How we make our products reflects our overall philosophy of continuous environmental improvement

HOW IT'S USED

Our thermoplastics play an important role in advancing human well-being, energy conservation and quality of life

These suggestions and data are based on information we believe to be reliable. They are offered in good faith, but without guarantee, as conditions and methods of use are beyond our control. We recommend that the prospective user determines the suitability of our materials and suggestions before adopting them on a commercial scale.

© 2024 PLASKOLITE, LLC 042024
OPTIX® is a registered trademark of Plaskolite LLC

PLASKOLITE

400 W Nationwide Blvd, Suite 40C
Columbus, OH 43215
800.848.9124 • Fax: 877.538.0754
plaskolite@plaskolite.com
www.plaskolite.com

FAB007_OPX_L